

Microscopic Oscillations in the Quantum Nucleation of Vortices Subject to Periodic Pinning Potential in a Thin Superconductor

Roberto Iengo

*International School for Advanced Studies, Via Beirut 4, 34014 Trieste (Italy)
and INFN – Sezione di Trieste, 34100 Trieste (Italy)*

Giancarlo Jug

*INFN and Istituto di Scienze Matematiche, Fisiche e Chimiche
Università di Milano a Como, Via Lucini 3, 22100 Como (Italy)
and INFN – Sezione di Pavia, 27100 Pavia (Italy)
(23 October 1995)*

We present a theory for the decay of a supercurrent through nucleation of vortex-antivortex pairs in a two-dimensional superconductor in the presence of dissipation and of a periodic pinning potential. Through a powerful quantum electrodynamics formulation of the problem we show that the nucleation rate develops oscillations in its current-density dependence which are connected to the pinning periodicity. A remnant of the dissipation-driven localization transition is present, and an estimate of the nucleation rate suggests that these effects might be observable in real thin superconductors.

PACS numbers: 74.60.Ge, 74.20.-z, 03.70.+k

There has been a strong revival of interest, recently, in the physics of magnetic vortices in type II and high-temperature superconductors [1]. Phenomena involving such vortices pose well-defined problems which are of great importance in the technological applications of the new high- T_c materials. Of particular interest are the statics (the vortex-glass transition) and dynamics (flux creep, vortex tunneling) of vortex systems in the presence of pinning impurity centers and an externally applied supercurrent. Most of these issues are connected with the residual resistance due to the thermal or quantum motion of the vortices and as hindered by the presence of pinning centers.

In a recent article, [2] we have pointed out that such residual resistance should develop even in the absence of an applied magnetic field. This is due to the spontaneous nucleation in the bulk of vortex-antivortex pairs induced, in the presence of a supercurrent driven by an external source, by the electromagnetic-like Magnus force acting on the quantum-mechanical vortices thought of as electron-positron-like pairs. This quantum nucleation occurs homogeneously throughout the sample. Exploiting this analogy with quantum electrodynamics (QED), a powerful “relativistic” quantum field theory (QFT) approach has been set up to study vortex nucleation in the two-dimensional (2-D) geometry and in the presence of quantum dissipation and of infinite barrier-height pinning centers. The central result is that the nucleation rate Γ has a strong exponential dependence on the number current density J , given by $\Gamma \propto \eta^{1/2} \eta_{eff} J^{-1} \exp\{-\eta_{eff} \mathcal{E}_{0R}^2 / 4\pi J^2\}$. Here, η_{eff} is an effective viscosity coefficient as renormalised by the magnetic-like part of the Magnus force, and $\mathcal{E}_{0R}$ is the rest or nucleation energy of a single vortex as renor-

malized by screened Coulomb interactions and (fake) Landau-level corrections. This exponential dependence would make the vortex nucleation (folded, e.g., into the sample’s resistance) observable in a rather narrow range of J -values (see below). We stress that whilst the possibility of homogeneous vortex nucleation as a decay mechanism for a supercurrent was independently and first proposed by Ping Ao, [3] the extension to dissipative dynamics, leading to qualitatively different results, was first treated in our recent paper, [2] to which the interested reader is referred for details of the formalism.

In this Letter we extend our formulation to the important situation in which finite barrier-height pinning centers are present and we initially envisage a geometry in which the pinning potential is periodic, with a lattice spacing $d = 2\pi/k$ and finite amplitude U_0 . We estimate the order of magnitude of the production rate Γ to find that under reasonable conditions the nucleation phenomenon ought to be observable. Moreover, we show that a remnant of the dissipation-induced vortex localization transition [4,5] is present through a J -dependence of Γ in which microscopic (or, depending on d , mesoscopic) oscillations are noted, due to the underlying periodicity of the pinning potential, and might also be observable under suitable conditions. Beside spontaneous bulk nucleation in the absence of a magnetic field, our formalism and results can also be applied to vortex tunneling from the edge, extending the work of Ref. [6–8] with the aim of obtaining an explicit formula, complete of prefactors, for the tunneling rate. Details of our calculations for the periodic pinning potential and the treatment for the edge tunneling problem will be presented elsewhere.

We begin by summarising the problem at hand, essentially a single-particle one, through the classical equation

of motion for the vortex moving in the $(x - y)$ plane of a 2-D superconducting film with a current flowing in the y -direction:

$$m\ddot{\mathbf{q}} = -\nabla U(\mathbf{q}) + e\mathbf{E} \cdot \mathbf{q} - e\dot{\mathbf{q}} \times \mathbf{B} - \eta\dot{\mathbf{q}} \quad (1)$$

Here, $m \rightarrow 0$ is the inertial mass of the vortex of topological charge $e = \pm 1$ and 2-D coordinate $\mathbf{q}(t)$ subject to the Magnus force having an electric-like $\mathbf{E} = 2\pi J\hat{\mathbf{x}}$ as well as a magnetic-like $\mathbf{B} = 2\pi^2\rho_s s\hat{\mathbf{z}}$ (ρ_s being the superfluid 3-D number density and s the film thickness). The e.m. current density J^{em} flowing through the sample's cross section is related to the number current density via $J = J^{em}s/2e$. We work in the units system in which $\hbar = 1$. Also, η is the friction coefficient and $U(\mathbf{q})$ the phenomenological periodic pinning potential which for convenience we take to be of the cosine form with wavenumber $\mathbf{Q} = (k, k)$: [11]

$$U(\mathbf{q}(t)) = U_0 \sum_{a=1}^D [1 - \cos(kq_a(t))] \quad (2)$$

The quantum-mechanical version of Eq. (1) is attained through the Feynman path-integral (FPI) transposition in which dissipation is treated quantistically through the formulation due to Caldeira and Leggett. [9] Particle nucleation (closely related to tunneling) is dealt with through a scalar-QED, 2-D version of Schwinger's calculation for the vacuum decay rate Γ in the presence of the crossed uniform fields $(\mathbf{E}, \mathbf{B})$. The formula for Γ reads [2]

$$\frac{\Gamma}{L^D} = \frac{2}{L^D T} Im \int_{\epsilon}^{\infty} \frac{d\tau}{\tau} e^{-\mathcal{E}_0 \tau} \int \mathcal{D}q(t) \exp\{-\int_0^{\tau} dt \mathcal{L}_E\} \quad (3)$$

where $L^D T$, with $D = 2$ here, is the space-time volume of the sample, $\mathcal{E}_0$ is the vortex nucleation energy, and the Euclidean single-particle Lagrangian for closed trajectories in space-time is

$$\mathcal{L}_E = \frac{1}{2}m_{\mu}\dot{q}_{\mu}\dot{q}_{\mu} - \frac{1}{2}i\dot{q}_{\mu}F_{\mu\nu}q_{\nu} + V(\mathbf{q}) + \sum_k \left\{ \frac{1}{2}m_k\dot{\mathbf{x}}_k^2 + \frac{1}{2}m_k\omega_k^2 \left(\mathbf{x}_k + \frac{c_k}{m_k\omega_k^2}\mathbf{q} \right)^2 \right\} \quad (4)$$

Here, the set of $\{\mathbf{x}_k\}$ represents the Caldeira-Leggett bath of harmonic oscillators simulating quantum friction, with $\frac{\pi}{2} \sum_k \frac{c_k^2}{m_k\omega_k} \delta(\omega - \omega_k) = \eta\omega \exp(-\omega/\Omega)$ (Ω being some frequency cutoff) fixing the spectral distribution of frequencies (we restrict the present discussion to the ohmic case). Also, $F_{\mu\nu}$ is the uniform Magnus field tensor and $V(\mathbf{q}) = 2\mathcal{E}_0 U(\mathbf{q})$ is the relativistic QFT counterpart of the classical potential, Eq. (2), thus having amplitude $A_0 = 2\mathcal{E}_0 U_0$ (we have assumed $A_0/\mathcal{E}_0^2 \ll 1$). Also, $m_3 = \frac{1}{2}$ and $m_1 = m_2 = \frac{\gamma}{2}$ with $\frac{1}{\gamma} = \mathcal{E}_0/m \rightarrow \infty$ playing the role of

the square of the speed of light in this formalism, where the non-relativistic limit corresponds to the overdamped case (which we consider).

Before delving into the evaluation of the FPI in Eq. (3), we briefly dwell on the physics of the problem at hand in the absence of the Magnus force, and on the meaning of Eq. (3). As is well-known, [4,5] the motion of a quantum particle in a periodic potential in the presence of friction displays a localization transition whereby for $\eta < \eta_c$ the particle is mobile whilst for $\eta > \eta_c$ it is confined, $\eta_c = k^2/2\pi = 2\pi/d^2$ being a sharp threshold independent of the potential's amplitude A_0 . This is reproduced by our formalism, with $\mathbf{E} = \mathbf{B} = 0$ and $\gamma \rightarrow 0$ in Eq. (4), with the confined phase treated within the variational "blocked-renormalization" scheme first introduced by Fisher and Zwerger, [10] through which a "mass" is dynamically generated for the damped modes' propagator. When the Magnus force-field is turned on (at least its electric-like part) a pole develops in the bare propagator, signalling the onset of mobility for all values of η . This divergence is in turn embedded in the formula for the pair production rate, Eq. (3). This one comes from a formulation of vortex nucleation [2] in terms of a scalar quantum field ϕ with QFT Lagrangian

$$\mathcal{L}(\phi) = D_0\phi^* D_0\phi - \frac{1}{\gamma}\mathbf{D}\phi^* \cdot \mathbf{D}\phi - (\mathcal{E}_0^2 + V(\mathbf{q}))\phi^*\phi \quad (5)$$

where $D_{\mu} = \partial_{\mu} - ieA_{\mu}$ with $A_{\mu} = \frac{1}{2}F_{\mu\nu}q_{\nu}$, in which the process of particle-antiparticle pair production is quite naturally encoded. In this QFT formulation, the vacuum decay rate is computed through the FPI on all closed loops in space-time weighted with the single-particle Euclidean Lagrangian corresponding to (5).

We now come to the evaluation of Γ , in the presence of the periodic potential which calls for a renormalization group (RG) type approach. Indeed, apart from the subtle question of dynamic mass generation for $\eta > \eta_c$, the problem at hand is that of a sine-Gordon-like model in (1+0) dimensions. Integrating out the Euclidean "time"-like component $q_3(t)$, we reach a formulation in which the electric-like and the magnetic-like Magnus field components are disentangled. In terms of Fourier components $\bar{\mathbf{q}}_n = \bar{\mathbf{q}}(\omega_n)$, with $\omega_n = 2\pi n/\tau$:

$$\int_0^{\tau} dt \mathcal{L}_E(q_{\mu}) \rightarrow \int_0^{\tau} dt \mathcal{L}_E(\mathbf{q}) = \tau \sum_{n \neq 0} \left\{ \frac{1}{4}\gamma\omega_n^2 + \frac{1}{2}\eta|\omega_n| - E^2\delta_{a1}\right\} \bar{q}_a(\omega_n)\bar{q}_a(-\omega_n) + \int_0^{\tau} dt V(\mathbf{q}) + \text{magn. part} \quad (6)$$

In this paper, we take the stance that the only role of the magnetic-like field in the presence of dissipation is to renormalize the nucleation energy, $\mathcal{E}_0^2 \rightarrow \mathcal{E}_{0R}^2 = \mathcal{E}_0^2 + \frac{1}{\gamma}\sqrt{\eta^2 + B^2}$, as well as the friction coefficient, $\eta \rightarrow \eta_{eff} = (\eta^2 + B^2)/\eta$ (denoted by η in what follows). This was indeed one of the main results of our investigation, [2] and

it amounts to an effective reduction of the D -dimensional problem to a one-dimensional system in the presence of the sole electric-like field. [8] A crucial role is played by dissipation, of course, as otherwise we would be confronted with the Azbel-Hofstadter problem in the presence of both periodic pinning and magnetic field. The evaluation of the FPI proceeds by means of the integration over the zero-mode, $\bar{q}_0$, and the high-frequency modes, $\bar{q}_n$ with $n > 1$, where we take the point of view that, as for the free particle in the uniform field, [2] the leading term in Γ comes from the divergence of the FPI associated with the lowest mode coupling to $\mathbf{E}$. We apply this scheme to the formula for the rate, Eq. (3), where the effective 1-D Lagrangian is the same as Eq. (6), with $\gamma = 0$ and renormalized $\mathcal{E}_0$ and η , and taking $q_1 \equiv q$ to be strictly a one-dimensional coordinate.

The effect of the modes $\bar{q}_n$ with $n > 1$ is taken into account through a frequency-shell RG-like argument by which, for the interesting $\eta > \eta_c$ case, these modes simply renormalize A_0 and are integrated out as effectively “massive” [10], that is via a Lagrangian $\mathcal{L}(\bar{q}_n) = \tau \left(\frac{1}{2} \eta |\omega_n| + M^2 - E^2 \right) \bar{q}_n \bar{q}_n^*$ (we will see below that at the relevant singularity $E^2 = \frac{1}{2} \eta |\omega_1|$, so that effectively $n \rightarrow n - 1$). The result of this integration is an additional, entropy-like renormalization of the activation energy, to be included in $\mathcal{E}_{0R}$, beside the renormalization of A_0 . Notice that in the mobile phase, $\eta < \eta_c$, the pinning potential’s amplitude would renormalize to zero, suppressing the oscillations (to be discussed below) in the vortex nucleation rate. We are therefore left with the integration over the modes $\bar{q}_0$ and $\bar{q}_1$, with a potential term

$$- \int_0^\tau dt V_R(q_0, q_1(t)) = A_{0R} \int_0^\tau dt \cos k(q_0 + q_1(t)) - A_0 \tau \simeq A_{0R} \tau J_0(2k|\bar{q}_1|) \cos kq_0 - A_0 \tau \quad (7)$$

In this equation, J_0 is the Bessel function and the new amplitude A_{0R} , as renormalised by the “blocked” $n > 1$ modes in the confined $\eta > \eta_c$ phase, is given by

$$A_{0R} = \begin{cases} A_0 \left(\frac{\Omega\tau}{2\pi} \right)^{-\eta_c/\eta} & \text{if } \eta < \eta_c \\ A_0 \left(\frac{\mu+1}{\mu+n^*-1} \right)^{-\eta_c/\eta} & \text{if } \eta > \eta_c \end{cases} \quad (8)$$

where we take the cutoff integer $n^*(\tau) = [\Omega\tau/2\pi] \gg 1$ and a dimensionless mass $\mu = \frac{2M^2}{\Omega\eta} = \left(\frac{2\pi A_0 \eta_c}{\Omega\eta} \right)^{\eta/\eta - \eta_c}$ has been introduced. Notice that, from the variational approach, $\mu = 0$ for $\eta < \eta_c$. Also, in Eq. (7) the phase of the $\bar{q}_1$ mode has been integrated out (a procedure generating an expansion controlled by the non-divergent amplitude A_{0R}), allowing us to integrate out the $\bar{q}_0$ -mode exactly. This leads to the expression

$$\frac{\Gamma}{2L^2} = Im \int_\epsilon^\infty d\tau \mathcal{N}(\tau) e^{-(\mathcal{E}_{0R}^2 + A_0)\tau} \times \int_0^\infty d|\bar{q}_1|^2 e^{-(\pi\eta - E^2\tau)|\bar{q}_1|^2} I_0(A_{0R}\tau J_0(2k|\bar{q}_1|)) \quad (9)$$

where $\mathcal{N}(\tau)$ is a suitable normalization factor and I_0 is the modified Bessel function. The vortex nucleation rate, therefore, bears some sign of the friction-driven localization transition, through $A_{0R}\tau$ as given by Eq. (8). It is clear that the singularity in τ from the $\bar{q}_1$ -integral occurs at $\tau_1 = \pi\eta/E^2$; taking a suitable $i\epsilon$ prescription [2] we get

$$\frac{\Gamma}{2L^2} = \frac{\mathcal{N}(\tau_1)}{4\pi J^2} e^{-(\mathcal{E}_{0R}^2 + A_0)\eta/4\pi J^2} I_0 \left(\frac{A_{0R}\eta}{4\pi J^2} J_0(2k\ell_N) \right) \quad (10)$$

where we have set $E = 2\pi J$. The presence of the $J_0(2k\ell_N)$ argument in the correction factor due to the pinning lattice thus gives rise to oscillations in Γ (hence in the sample’s resistance) through the parameter $2k\ell_N = 4\pi\ell_N/d$. Vortex nucleation (or tunneling) is therefore sensitive to the corrugation of the pinning substrate.

In order to compute the nucleation length ℓ_N we have used a saddle-point procedure in Eq. (9), noticing that for large τ : $I_0(x\tau) \rightarrow \frac{1}{\sqrt{2\pi|x|\tau}} e^{|x|\tau}$. This leads to a self-consistent equation, $\mathcal{E}_{0R}^2 + A_0 - A_{0R}|J_0(2k\ell_N)| = 4\pi^2 J^2 \ell_N^2$, which we solve to first order, neglecting corrections for small J :

$$\ell_N^2 \simeq \frac{\mathcal{E}_{0R}^2 + A_0}{4\pi^2 J^2} - \frac{A_{0R}}{4\pi^2 J^2} \left| J_0 \left(k \frac{\sqrt{\mathcal{E}_{0R}^2 + A_0}}{\pi J} \right) \right| \quad (11)$$

As for the normalization factor $\mathcal{N}(\tau_1)$, we get (e is here Euler’s number)

$$\mathcal{N}(\tau_1) = \frac{e^2}{16\pi^2} n^*(\tau_1) (1 + \mu) (1 + \mu n^*(\tau_1)) (\pi/\tau_1)^{3/2} \eta^2 \quad (12)$$

Our final expression for the rate Γ (with ℓ_N given by Eq.(11)) is

$$\begin{aligned} \Gamma &= \Gamma_0 K(J) \\ \frac{\Gamma_0}{L^2} &= \frac{e\Omega\eta^{3/2}}{32\pi^2 J} e^{-(\mathcal{E}_{0R}^2 + A_0)\eta/4\pi J^2} \\ K(J) &= e(1 + \mu) \left(1 + \frac{\mu\Omega\eta}{8\pi^2 J^2} \right) I_0 \left(\frac{A_{0R}\eta}{4\pi J^2} J_0(2k\ell_N) \right) \end{aligned} \quad (13)$$

where $K(J)$ is the oscillating correction factor due to the pinning substrate.

So far, the computation referred to $T = 0$. In [2] we proposed to take into account finite temperatures by adding incoherently, in the above formulas, a term proportional to T (note $k_B = 1$): $J^2 \rightarrow J^2 + \frac{\eta\mathcal{E}_{0R}}{8\pi} T$, such that for $J \rightarrow 0$ the standard Boltzmann exponential form in the vortex density, $\rho_v \propto \sqrt{\Gamma}$, is recovered in the absence of pinning. This might be a reasonable qualitative treatment of thermal effects for temperatures less than $\approx 8\pi J^2/\eta\mathcal{E}_{0R}$. Furthermore, we propose, following Minnhagen [12], to

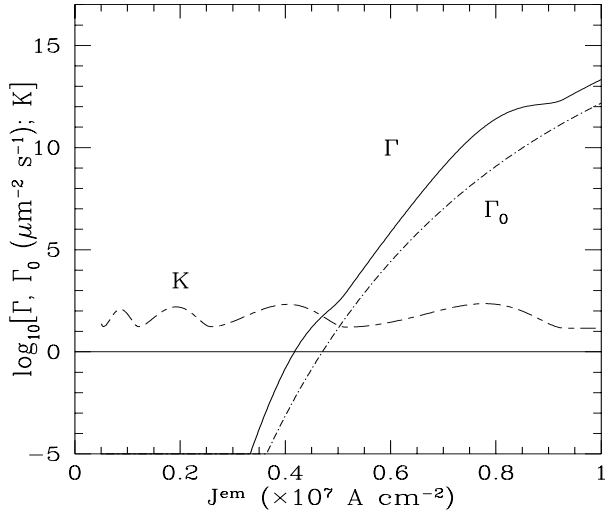


FIG. 1. Vortex-antivortex production rate (in $\mu\text{m}^{-2}\text{s}^{-1}$, $\log_{10}$ scale) in the presence (Γ) and absence (Γ_0) of the periodic pinning potential, versus current density J^{em} (in $\text{A cm}^{-2} \times 10^7$). $K(J)$ is the current-dependent correction factor due to the periodic substrate.

account for vortex-antivortex Coulomb-like interactions by means of a current-dependent (and temperature-independent) activation energy: $\mathcal{E}_R(J) = \mathcal{E}_{0R} \ln(J_{\text{max}}/J)$, with $\mathcal{E}_{0R}$ including all other renormalization effects. This expression entails an $\mathcal{E}_R$ infinite for $J = 0$ (as is appropriate below the Kosterlitz-Thouless (KT) transition in the film) and changing sign, thus becoming unphysical, at J_{max} .

For illustrative purposes, in order to estimate the parameters involved in our final expression for the rate Γ (Eq. (14)), we take J_{max} an order of magnitude higher than the single-crystal YBCO critical current, [13] namely $J_{\text{max}}^{\text{em}} = 10^8 \text{ A cm}^{-2}$, and take $\mathcal{E}_R \approx 80 \text{ K}$ for $J = 10^7 \text{ A cm}^{-2}$, of the order of magnitude of the KT transition temperature [1]. The important friction coefficient is taken to be $\eta \approx 10^{-2} \text{ \AA}^{-2}$, from the Bardeen-Stephen formula [14] applied to YBCO films. A most sensitive parameter is related to the amplitude of the pinning potential, $\epsilon = A_0/\mathcal{E}_{0R}^2$, which, like the pinning lattice spacing d , is entirely unknown. We have taken a negative $\epsilon = -0.5$, borrowing from classical nucleation the point of view that vortex production is actually aided by the presence of pinning centers. Finally, $d = 50 \text{ \AA}$ concludes our illustrative case which is clearly of the confined-phase type. As $\eta > \eta_c$, we have taken $\mu \approx 1$ and $A_{0R} \approx A_0$, for simplicity's sake, and find no significant dependence on the most uncertain of all parameters, Ω . Its dimensions being the same as $\mathcal{E}_0^2$, in Fig. 1 we have taken $\Omega = \mathcal{E}_{0R}^2/e$. Also, we take the film thickness $s = 10 \text{ \AA}$ as the typical interlayer spacing. This figure reports the pro-

duction rate, both in the absence and in the presence of the above-specified periodic pinning potential. We stress that, despite our possibly optimal choice of parameters, we believe that the order of magnitude of Γ is such as to make vortex nucleation observable within acceptable values for the current density of some high- T_c materials. When pinning is present, we predict for the first time the possibly observable oscillations of $\Gamma(J)$, reflecting the underlying pinning periodicity. This should produce microscopic oscillations in the measured resistance at relatively low temperatures ($T = 5 \text{ K}$ in Fig. 1). For higher temperatures, vortex nucleation would be essentially thermally activated and therefore outside the scope of the present investigation.

We hope that these findings will stimulate further research, both theoretical and experimental, on the quantum mechanics of vortices in thin superconducting films.

One of us (GJ) is grateful to the International School for Advanced Studies in Trieste, where part of this work was carried out, for hospitality and the use of its facilities.

-
- [1] For a recent survey of this field, see: G. Blatter, M.V. Feigel'man, V.B. Geshkenbein, A.I. Larkin and V.M. Vinokur, *Rev. Mod. Phys.* **66**, 1125 (1994); also, see the articles in: *Phase Transitions and Relaxation in Systems with Competing Energy Scales*, T. Riste and D. Sherrington (Ed.s) (Kluwer, Dordrecht 1993).
 - [2] R. Iengo and G. Jug, *Phys. Rev. B* **52**, 7536 (1995).
 - [3] P. Ao, *J. Low Temp. Phys.* **89**, 543 (1992).
 - [4] A. Schmid, *Phys. Rev. Lett.* **51**, 1506 (1983).
 - [5] F. Guinea, V. Hakim and A. Muramatsu, *Phys. Rev. Lett.* **54**, 263 (1985).
 - [6] P. Ao and D.J. Thouless, *Phys. Rev. Lett.* **70**, 2158 (1993).
 - [7] P. Ao and D.J. Thouless, *Phys. Rev. Lett.* **72**, 132 (1994).
 - [8] M.J. Stephen, *Phys. Rev. Lett.* **72**, 1534 (1994).
 - [9] A.O. Caldeira and A.J. Leggett, *Ann. Phys.* **149**, 374 (1983).
 - [10] M.P.A. Fisher and W. Zwerger, *Phys. Rev. B* **32**, 6190 (1985).
 - [11] We assume full isotropy in the potential, the extension to the anisotropic case being trivial.
 - [12] P. Minnhagen, *Rev. Mod. Phys.* **59**, 1001 (1987).
 - [13] M. Cyrot and D. Pavuna, *Introduction to Superconductivity and High- T_c Materials* (World Scientific, Singapore 1992).
 - [14] J. Bardeen and M.J. Stephen, *Phys. Rev.* **140**, 1197 (1965); see also: M. Tinkham, *Introduction to Superconductivity* (McGraw-Hill, New York 1975).